



Results from Air Force Investigation into 20mm Case Neck Separation

NDIA Joint Armaments Conference
14-17 May 2012

Patrick Gray
780 TS/OGMTG
Eglin AFB, FL



UNCLASSIFIED



Presentation Outline

- 20mm Case Neck Separation (CNS)
Description/Background
- Air Force Screening Operation
- Results/Path Forward
- Conclusions

UNCLASSIFIED



CNS Failure Description



- Tensile failure of M103 brass case in shoulder-neck region during firing
- Excessive loading stretches neck to failure
- Propagates around circumference of neck

UNCLASSIFIED



CNS Background

- 40-plus year history affecting all Services
- No root cause consensus
- Crimp groove most likely failure source
- Groove still present post-firing
- Projectile pulling case neck



UNCLASSIFIED



CNS Progression



UNCLASSIFIED



Gun System Damage


- Jams gun due to lack of case control
- “Soft” jam upon ammo download
- “Hard” jam with gun at max firing rate



UNCLASSIFIED



CNS Fragmentation

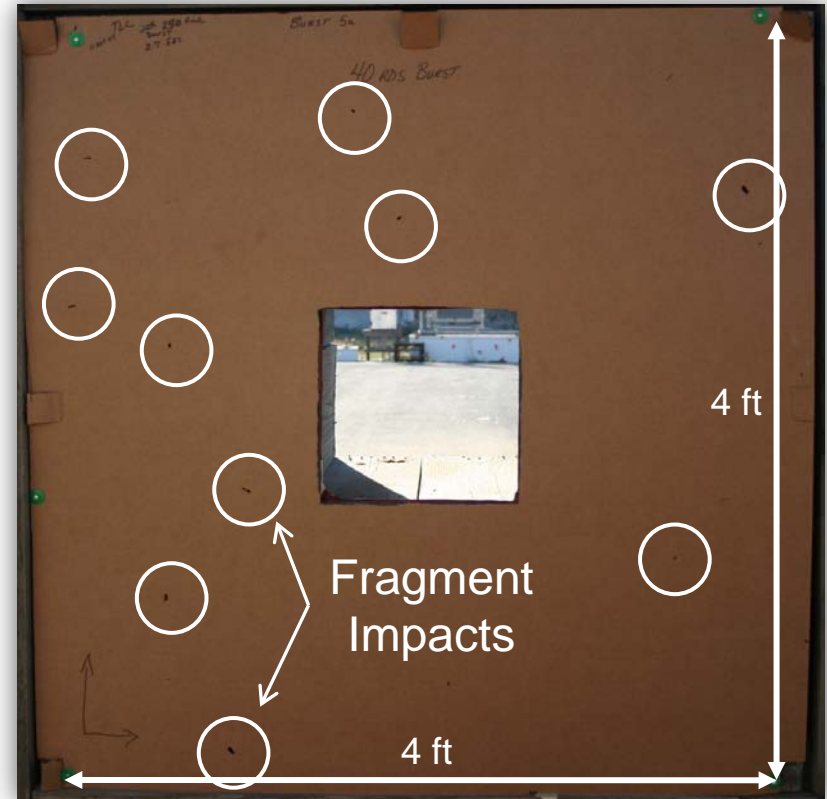

UNCLASSIFIED



F-16 AoA Probe Damage



Case Neck Fragment Impact

UNCLASSIFIED




Air Force Screening Operation

- Tasked to assess CNS potential in inventory
- Screen via case neck elongation measurement
 - Hypothesis – CNS-prone ammo elongates more
- ~ 200 lots subjected to projectile extraction, single shot and M61A1 burst firing
- Brass from all three tests measured
- 6 lots experienced CNS during test
- Lots assigned risk level 1-4

UNCLASSIFIED




M61A1 Elongation Profile

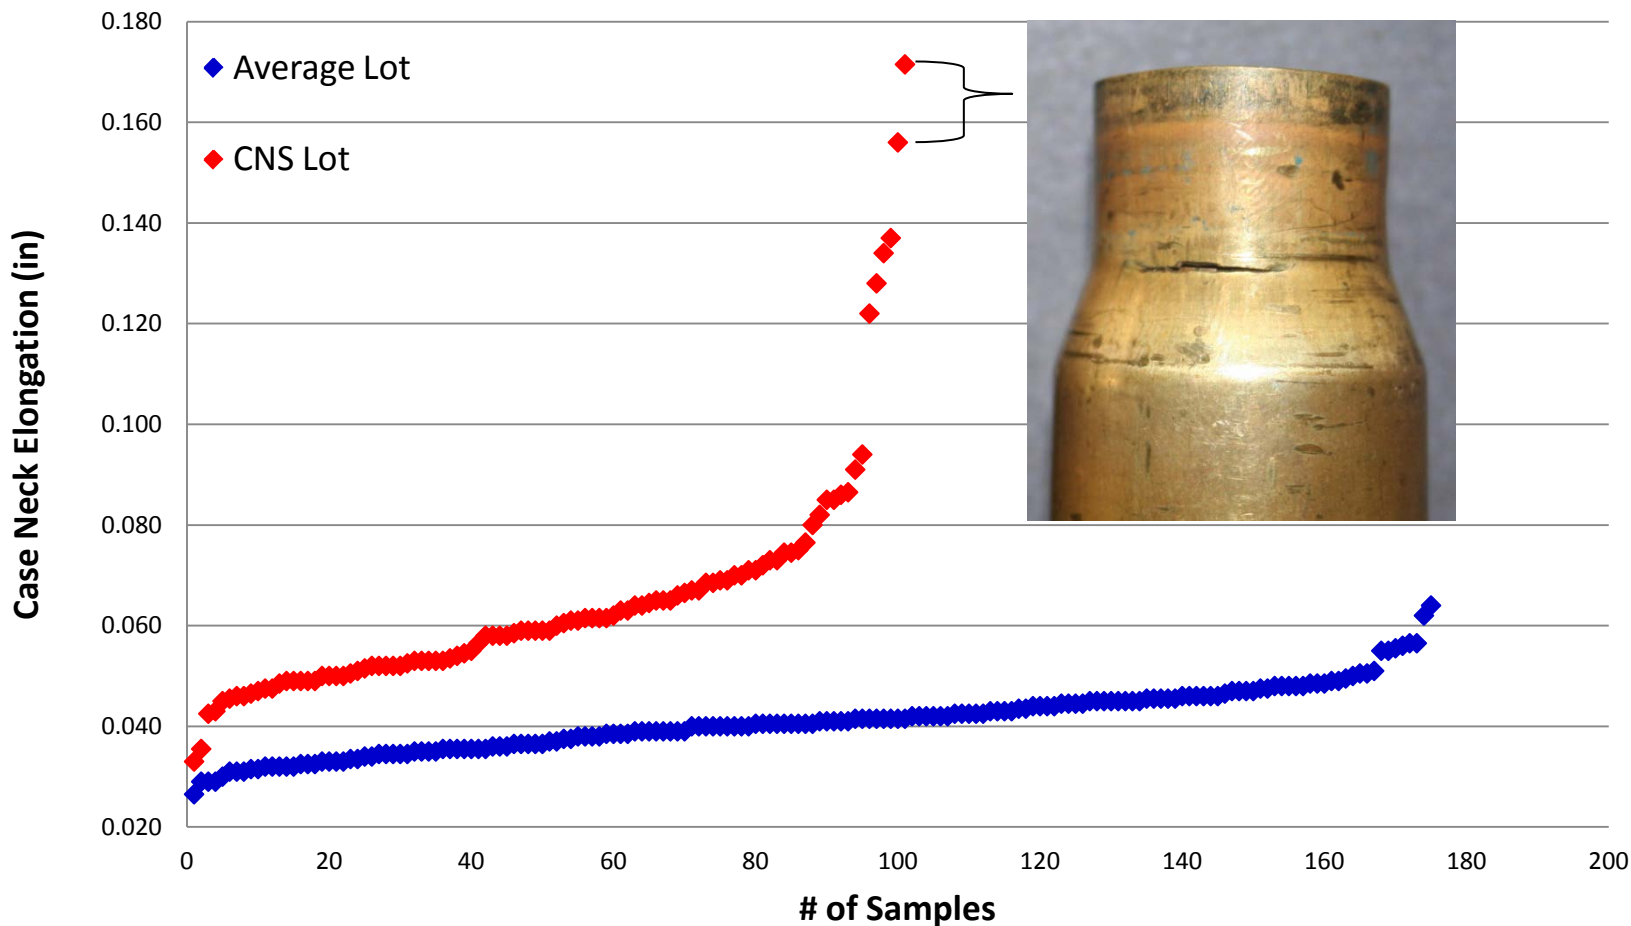

UNCLASSIFIED



Elongation vs Test Type

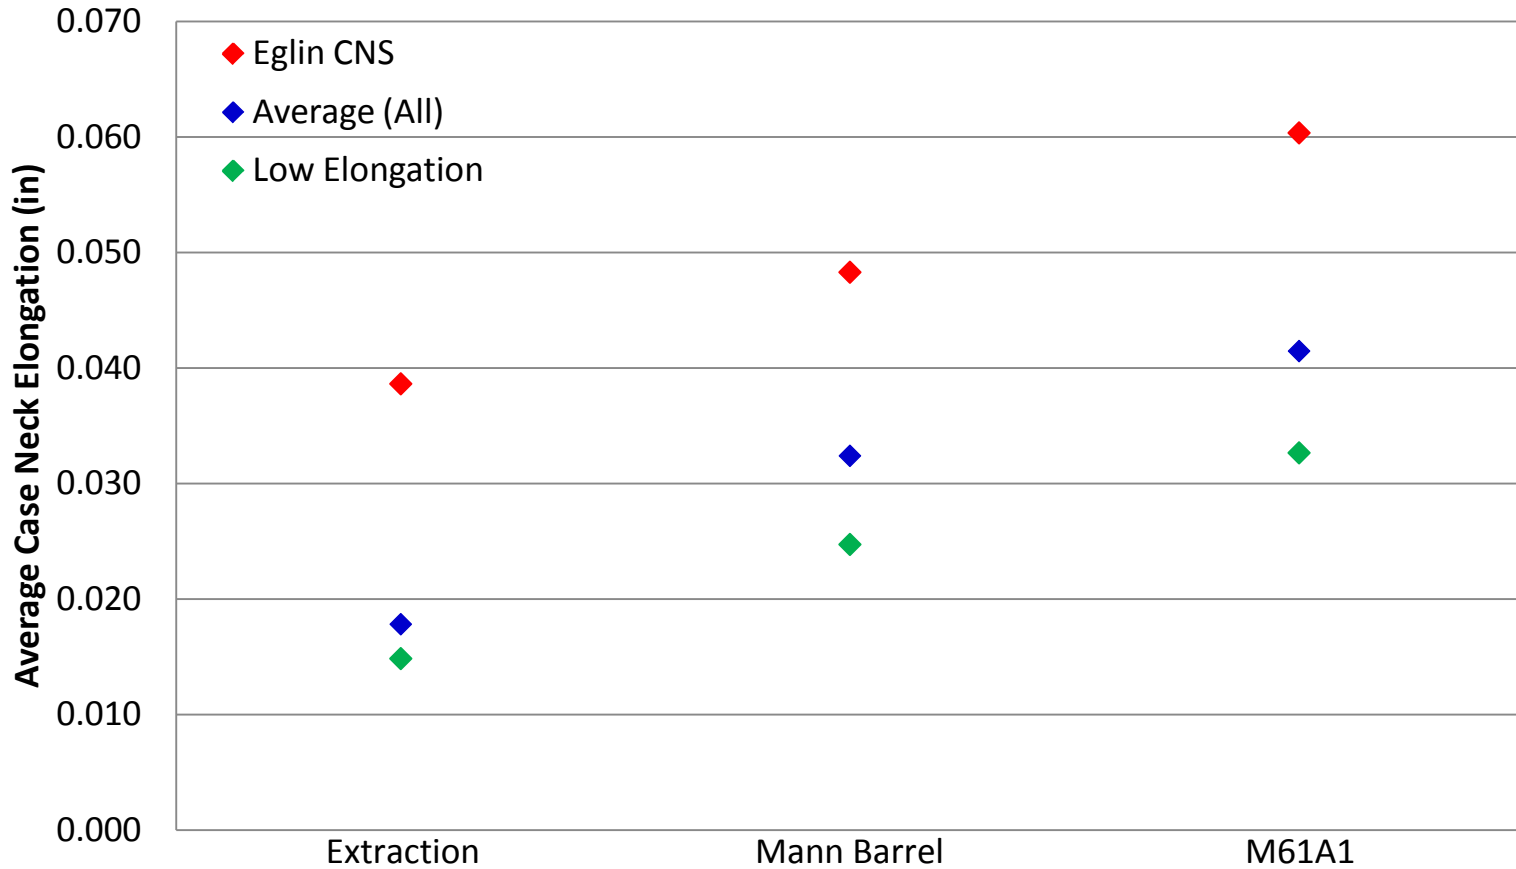

UNCLASSIFIED



Elongation/Extraction Force Comparison



Category	Avg M61A1 Elongation (in)	Max Extraction Force (lbs)	Avg Extraction Force (lbs)	Range (lbs)	Std Dev (lbs)
Eglin CNS Lots (6)	0.0603	2460	1932	1172	299
Average - All Lots (200)	0.0415	2021	1633	716	178
Low Elongation (5)	0.0320	1415	1179	359	99

Allowable Range: 1100-2800 pounds


- ~80% of 145+ historical CNS lots w/ max extraction force greater than 2000 lbs
- Sample average 2260 pounds

UNCLASSIFIED




Elongation vs Extraction Force

Lot -069

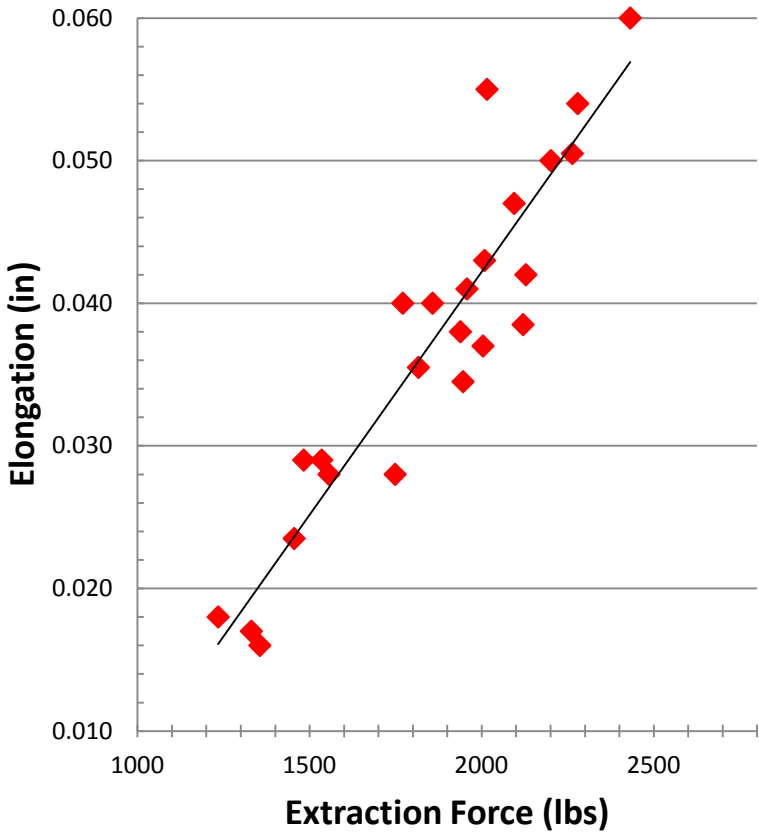

Lot -092

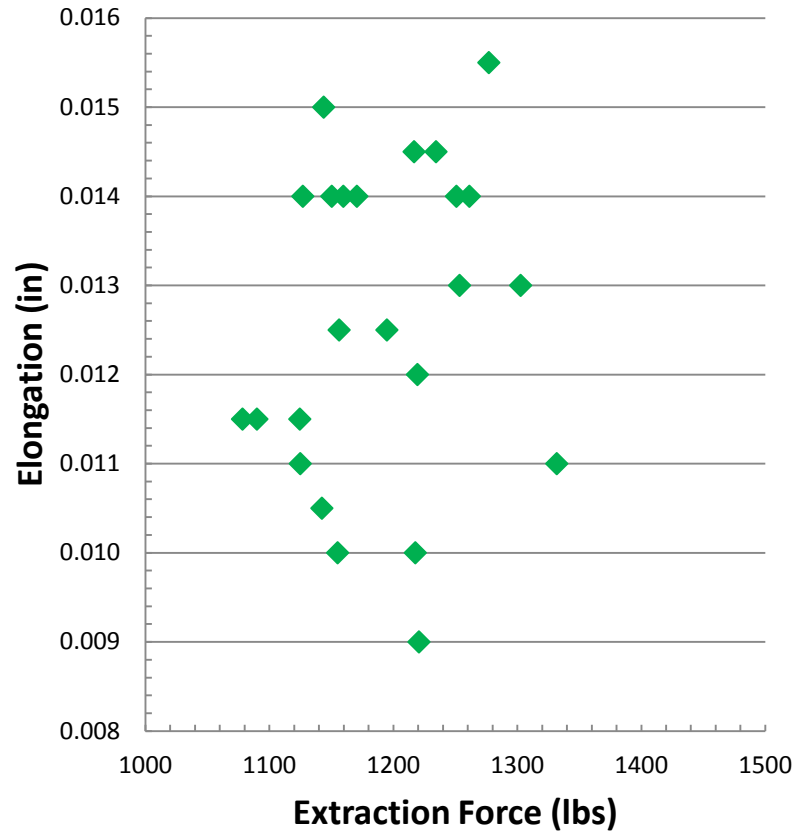


UNCLASSIFIED



20mm Cartridge Modifications


- Loctite sealant (2010)
 - Reduced extraction force variance
- Modified crimp groove (2012)
 - Shallower groove depth, less sharp radii
- Reduce 2800 lb upper limit – TBD

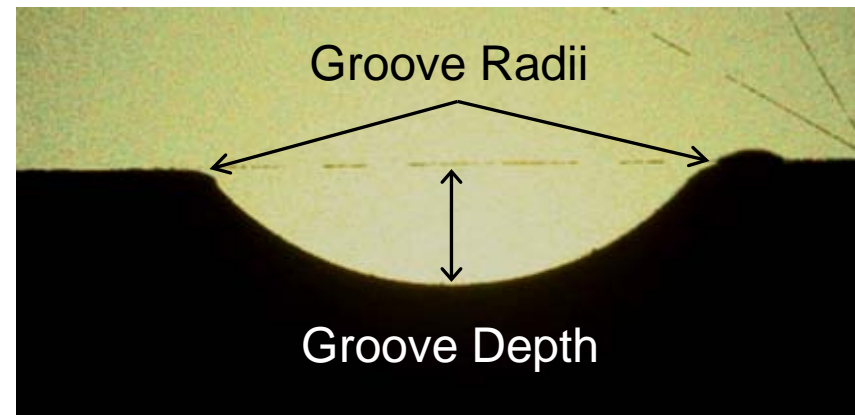

UNCLASSIFIED




Extraction Force vs Sealant

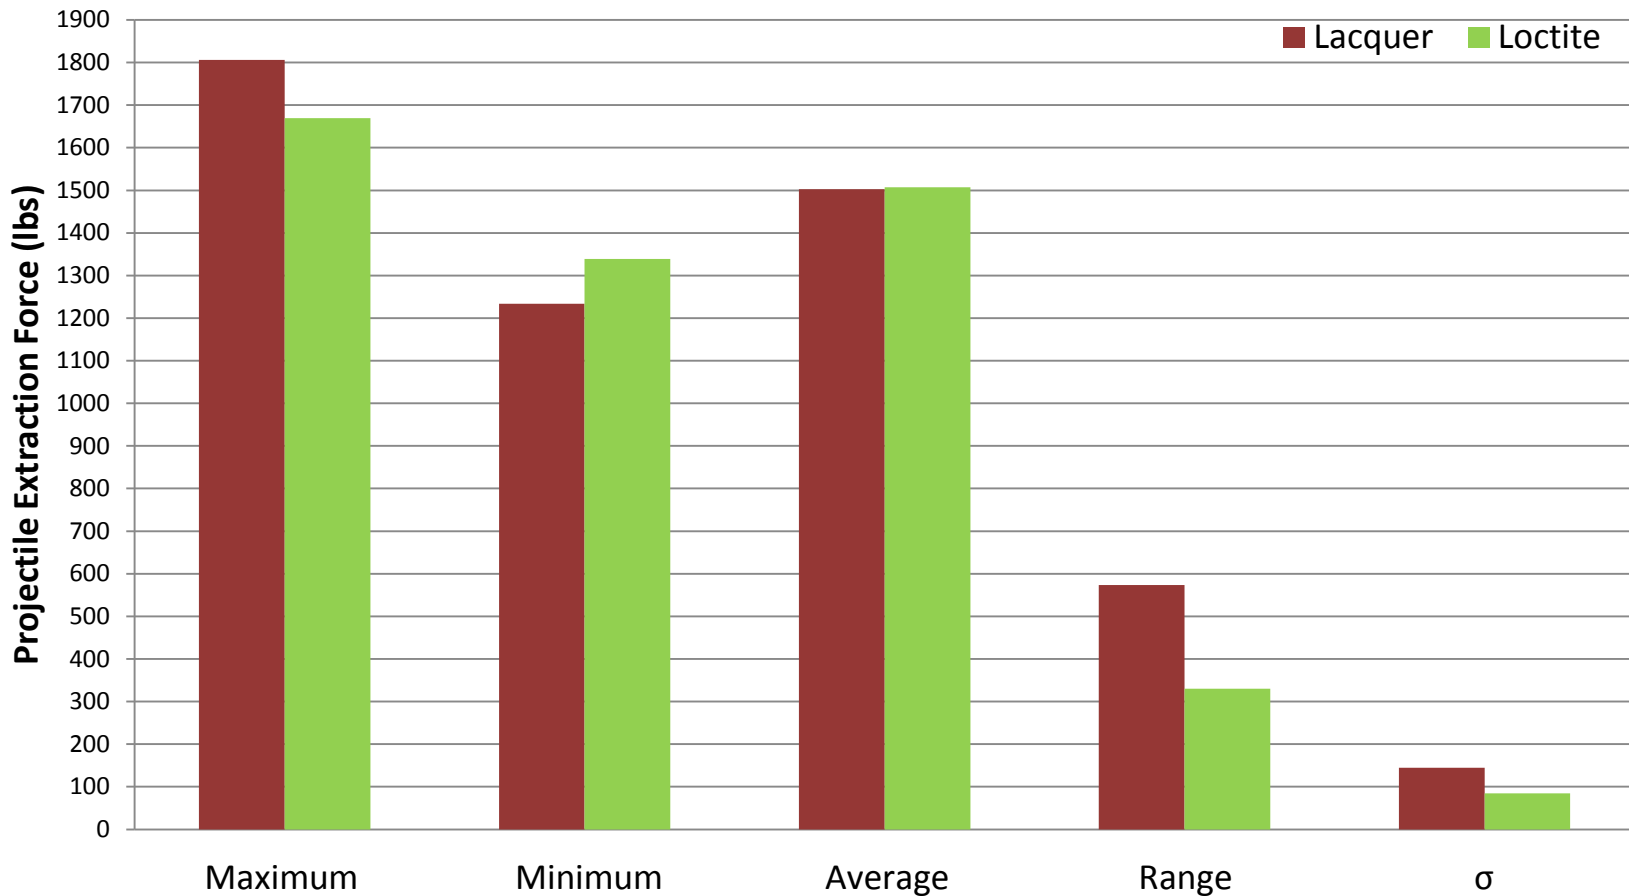

UNCLASSIFIED



Extraction Force vs “Configuration”

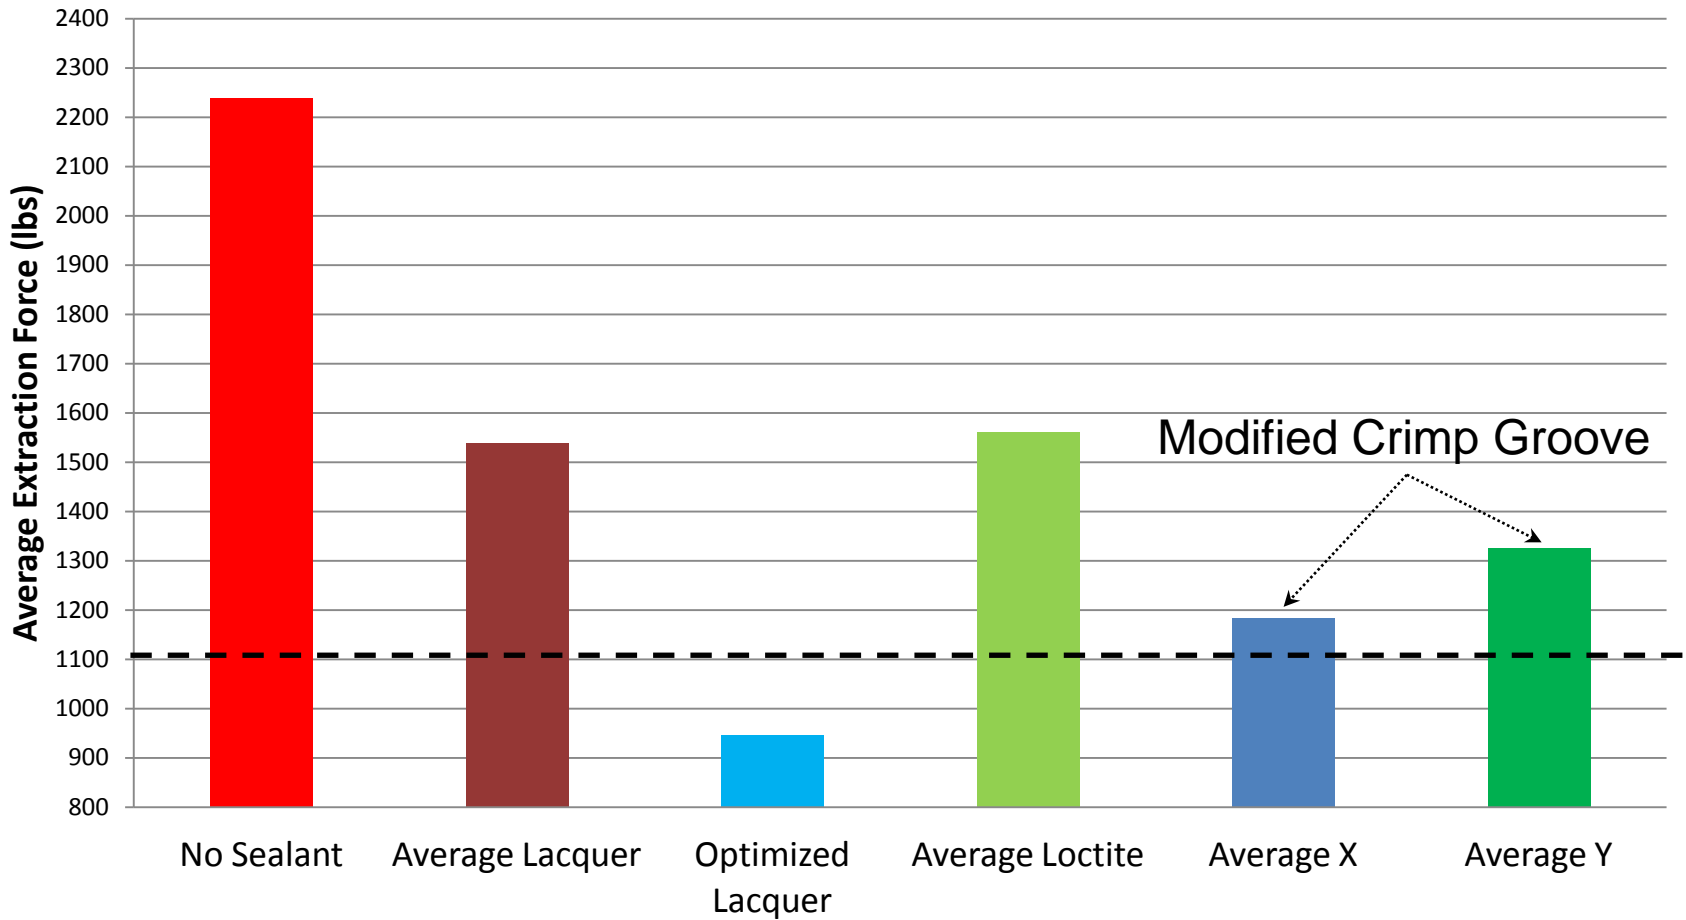

UNCLASSIFIED



Conclusions

- CNS lots elongate more than average lots
- Elongation correlated with extraction force
- Higher extraction forces present in majority of historical CNS lots
- Loctite/crimp groove modifications promising



Questions/Comments??



Contact Info

Patrick Gray (daniel.gray@eglin.af.mil)

Test Engineer, 780 TS/OGMTG

Comm: 850-882-9413, DSN 872-9413


UNCLASSIFIED

Backup Slides




Elongation vs Sample

Lot -086

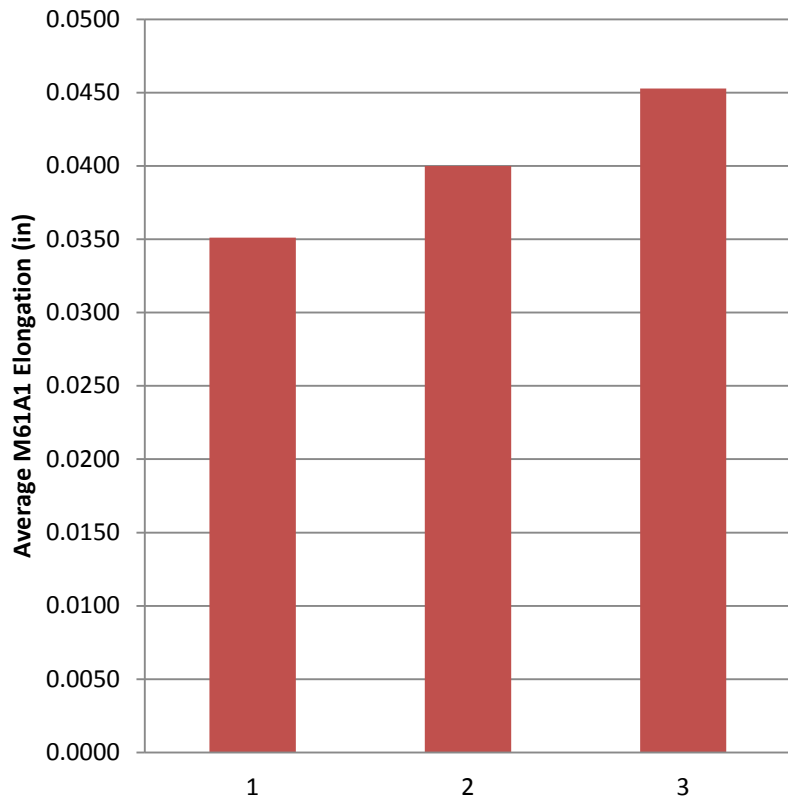

Lot -039

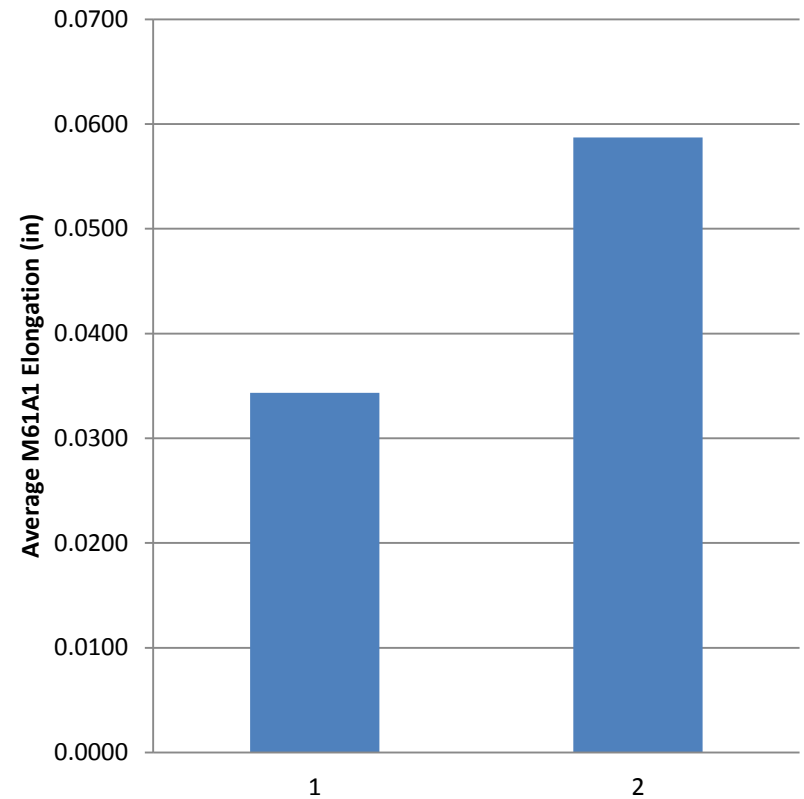


UNCLASSIFIED




Elongation vs Extraction Force



Lot -069

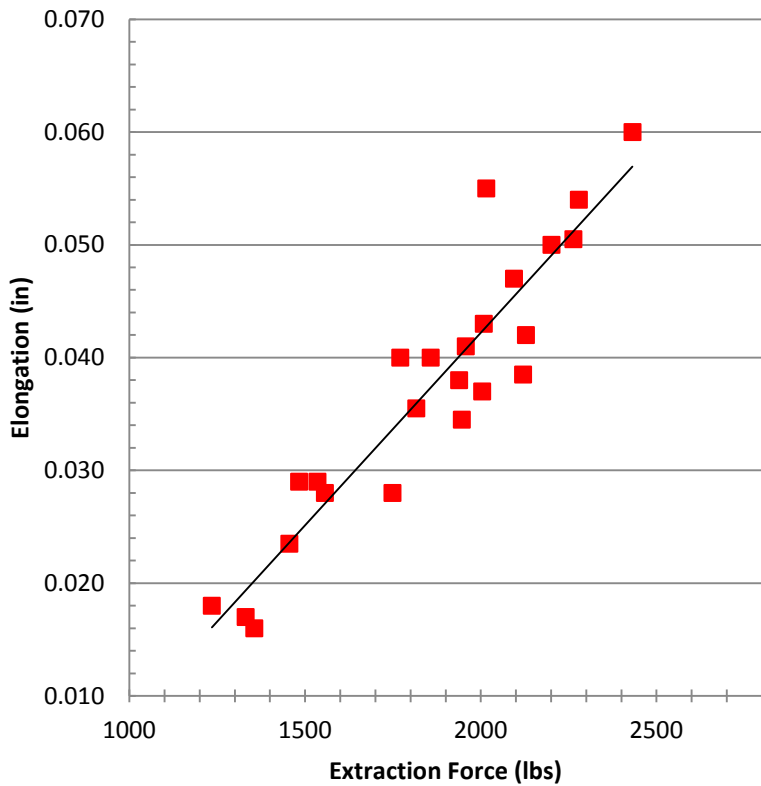

Lot -002 (Loctite)

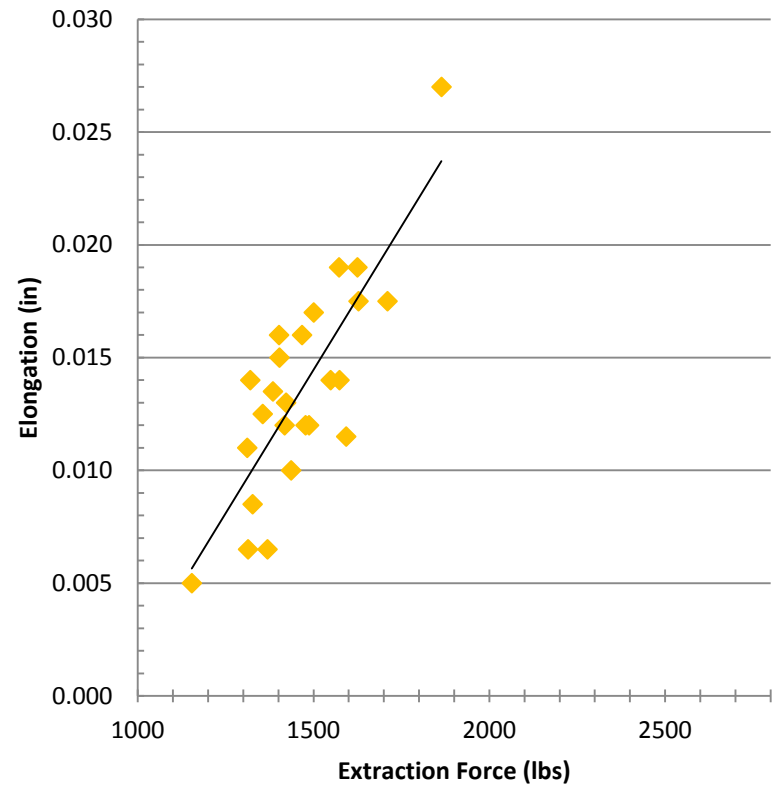


UNCLASSIFIED




Elongation vs Extraction Force



Lot -030

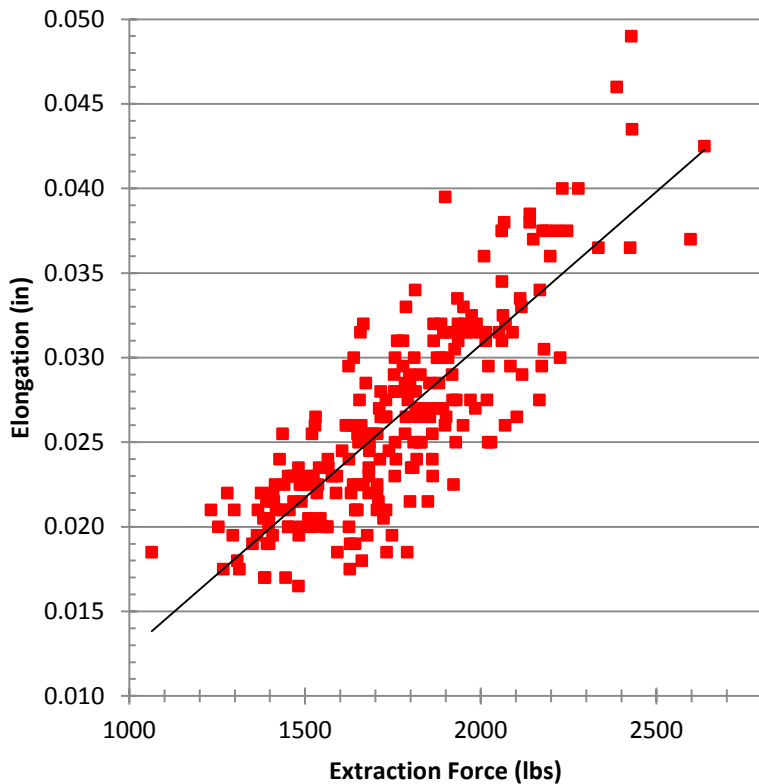

Lot -066

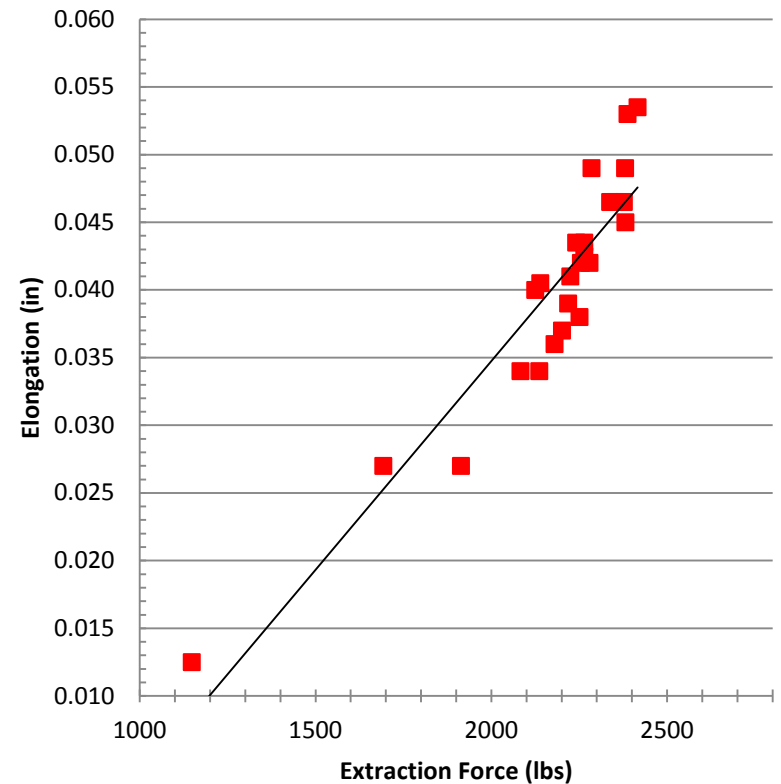

UNCLASSIFIED



Secondary CNS



- Result of primary failure
- Partial telescoping of advancing cartridge
- Smoother, mid-shoulder fracture surface
- No “dimpling”

UNCLASSIFIED